


101FR AWAPLAN PREMIUM FR

INSULATED DECKS

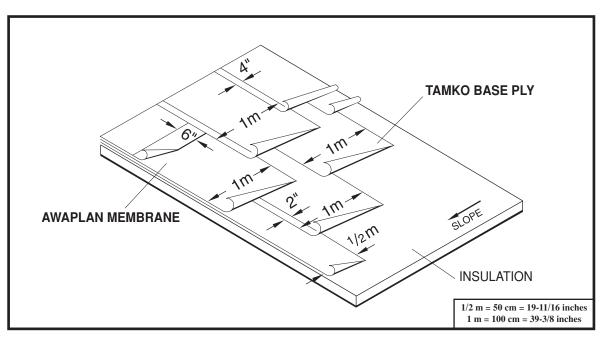

Material Requirements

TAMKO GLASS-BASE®, TAM-GLASS PREMIUM®,
TAM-PLY IV®, or BASE-N-PLY®
Fiberglass Sheet 1 ply
TAMKO AWAPLAN PREMIUM FR
(Granule Surfaced) 1 ply
Asphalt (Per 100 sq. ft.) Approx. 46 lbs.

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements.

Insulation: The insulation should be installed according to the manufacturer's specification in the thickness required. The insulation should conform to TAMKO requirements. Polyisocyanurate and expanded polystyrene must have an overlay of a minimum 1/2 in. fiberboard, perlite, or fiberglass roof insulation.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, **Type III for slopes up to 1/4 in.** and **Type IV for slopes up to 3 in.**

Base Ply: Starting at the low point of the roof, install 1 layer of TAMKO GLASS-BASE, TAM-GLASS PREMIUM, TAM-PLY IV, or BASE-N-PLY beginning with a 1/2 m width, then a full 1 m width, side lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Solid mop to the insulation with approximately 23 lbs. (+15%) of specification asphalt per 100 sq. ft.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the base ply (pressed into the hot asphalt) with approximately 23 lbs. (±15%)

of specification asphalt per 100~sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the base ply by sufficiently heating the back side with a torch at the juncture of the base ply and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica and formaldehyde. Crystalline silica and formaldehyde have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.

Application of product(s) in this specification using "torch applied" or "hot mopped" applications may expose workers and others in the work area to oxidized asphalt and its emissions. The International Agency for Research on Cancer has classified occupational exposures to oxidized asphalt and its emissions during roofing as



101FR AWAPLAN PREMIUM FR


INSULATED DECKS

a "probable human carcinogen." During installation and removal of the product(s) in this specification, including "torch applied" or "hot mopped" application, workers must take precautions to assure adequate ventilation and use effective personal protective equipment to prevent exposures to dusts, fumes, vapors and mists. It is the responsibility of the contractor and workers to protect themselves and others in the work area from exposure to oxidized asphalt and its emissions when applying the product(s) in this specification.



102FR AWAPLAN PREMIUM FR

INSULATED DECKS

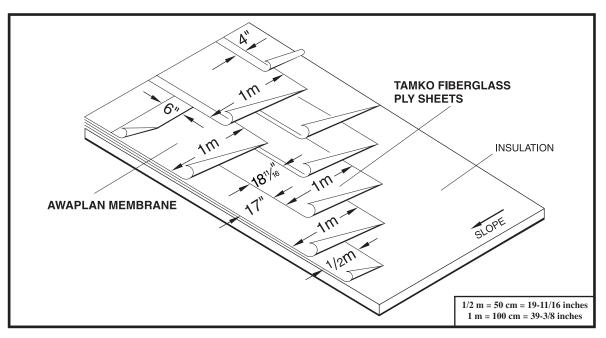

Material Requirements

TAMKO TAM-GLASS PREMIUM®, or TAM-PLY IV®
Fiberglass Ply Sheet 2 plies

TAMKO AWAPLAN PREMIUM FR
(Granule Surfaced) 1 ply
Asphalt (Per 100 sq. ft.) Approx. 69 lbs.

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements.

Insulation: The insulation should be installed according to the manufacturer's specification in the thickness required. The insulation should conform to TAMKO requirements. Polyisocyanurate and expanded polystyrene must have an overlay of a minimum 1/2 in. fiberboard, perlite, or fiberglass roof insulation.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, Type III for slopes up to 1/4 in. and Type IV for slopes up to 3 in.

Fiberglass Ply Sheet 2 Ply Installation: Over the insulation, install 2 plies of TAM-GLASS PREMIUM or TAM-PLY IV in specification asphalt. Starting from the low point of the roof, apply a 1/2 m width, then a full 1 m width. Follow with full 1 m widths, shingle fashion, lapping each ply 20-11/16 in. in such a manner so that at least 2 plies cover the insulation at any point. Approximately 23 lbs. $(\pm 15\%)$ of specification asphalt per 100 sq. ft. should be used to embed each ply.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the ply sheet (pressed into the hot asphalt) with approximately 23 lbs. (+15%) of specifica-

tion asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the ply sheet by sufficiently heating the back side with a torch at the juncture of the ply sheet and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica and formaldehyde. Crystalline silica and formaldehyde have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.

Application of product(s) in this specification using "torch applied" or "hot mopped" applications may expose workers and others in the work area to oxidized asphalt and its emissions. The International Agency for Research on Cancer has classified occupational exposures to oxidized asphalt and its emissions during roofing as a "probable human carcinogen." During installation and removal



102FR AWAPLAN PREMIUM FR


INSULATED DECKS

of the product(s) in this specification, including "torch applied" or "hot mopped" application, workers must take precautions to assure adequate ventilation and use effective personal protective equipment to prevent exposures to dusts, fumes, vapors and mists. It is the responsibility of the contractor and workers to protect themselves and others in the work area from exposure to oxidized asphalt and its emissions when applying the product(s) in this specification.



103FR AWAPLAN PREMIUM FR

INSULATED DECKS

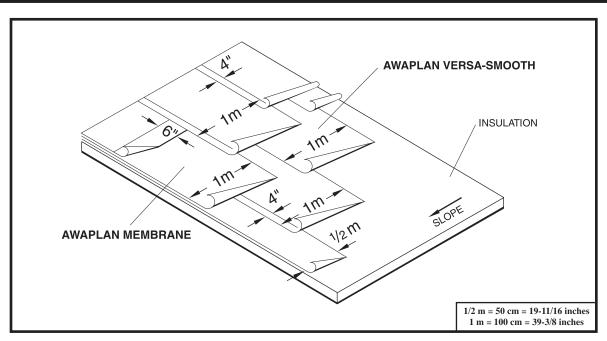

Material Requirements

TAMKO AWAPLAN VERSA-SMOOT	TH 1 ply
TAMKO AWAPLAN PREMIUM FR (Granule Surfaced)	1 ply
Asphalt (Per 100 sq. ft.)	Approx. 46 lbs.
Aspirant (1 cr 100 sq. 11.)	Approx. 40 lbs.

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements.

Insulation: The insulation should be installed according to the manufacturer's specification in the thickness required. The insulation should conform to TAMKO requirements. Polyisocyanurate and expanded polystyrene must have an overlay of a minimum 1/2 in. fiberboard, perlite, or fiberglass roof insulation.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, Type III for slopes up to 1/4 in. and Type IV for slopes up to 3 in.

AWAPLAN VERSA-SMOOTH: Starting at the low point of the roof, install 1 ply of TAMKO AWAPLAN VERSA-SMOOTH, beginning with a 1/2 m width, than a full 1 m width, side lapped 4 in. and end lapped 6 in. Apply at a right angle to the slope of the roof. The AWAPLAN VERSA-SMOOTH should be solidly adhered to the insulation (pressed into the hot asphalt) with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN VERSA-SMOOTH can be heat welded and should be solidly adhered to the insulation by sufficiently heating the back side with a torch at the juncture of the insulation and the AWAPLAN VERSA-SMOOTH roll to form a bead of melted asphalt as the AWAPLAN VERSA-SMOOTH is rolled out.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the base ply (pressed into the hot asphalt) with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the base ply by sufficiently heating the back side with a torch at the juncture of the base ply and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica. Crystalline silica has been classified as a "known" human carcinogen by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.




103FR AWAPLAN PREMIUM FR

INSULATED DECKS



104FR AWAPLAN PREMIUM FR

INSULATED DECKS

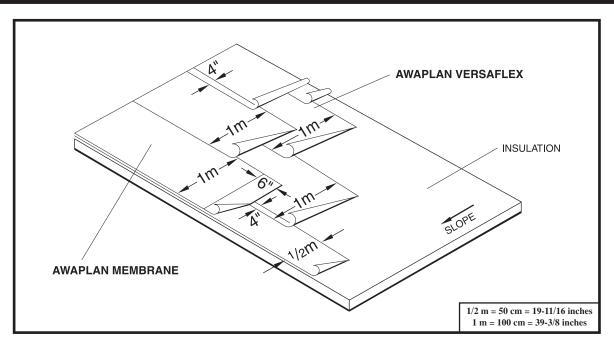

Material Requirements

TAMKO AWAPLAN VERSAFLEX	1 ply
TAMKO AWAPLAN PREMIUM FR	
(Granule Surfaced)	1 ply
Asphalt (Per 100 sq. ft.)	Approx. 46 lbs.

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements

Insulation: The insulation should be installed according to the manufacturer's specification in the thickness required. The insulation should conform to TAMKO requirements. Polyisocyanurate and expanded polystyrene must have an overlay of a minimum 1/2 in. fiberboard, perlite, or fiberglass roof insulation.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, **Type III for slopes up to 1/4 in.** and **Type IV for slopes up to 3 in.**

AWAPLAN VERSAFLEX: Starting at the low point of the roof, install 1 ply of TAMKO AWAPLAN VERSAFLEX, beginning with a 1/2 m width, then a full 1 m width, side lapped 4 in. and end lapped 6 in. Apply at a right angle to the slope of the roof. The AWAPLAN VERSAFLEX should be solidly adhered to the insulation (pressed into the hot asphalt) with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the base ply

(pressed into the hot asphalt) with approximately 23 lbs. ($\pm 15\%$) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the base ply by sufficiently heating the back side with a torch at the juncture of the base ply and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica. Crystalline silica has been classified as a "known" human carcinogen by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.

Application of product(s) in this specification using "torch applied" or "hot mopped" applications may expose workers and others in the work area to oxidized asphalt and its emissions. The Interna-



104FR AWAPLAN PREMIUM FR


INSULATED DECKS

tional Agency for Research on Cancer has classified occupational exposures to oxidized asphalt and its emissions during roofing as a "probable human carcinogen." During installation and removal of the product(s) in this specification, including "torch applied" or "hot mopped" application, workers must take precautions to assure adequate ventilation and use effective personal protective equipment to prevent exposures to dusts, fumes, vapors and mists. It is the responsibility of the contractor and workers to protect themselves and others in the work area from exposure to oxidized asphalt and its emissions when applying the product(s) in this specification.



107FR AWAPLAN PREMIUM FR

INSULATED DECKS

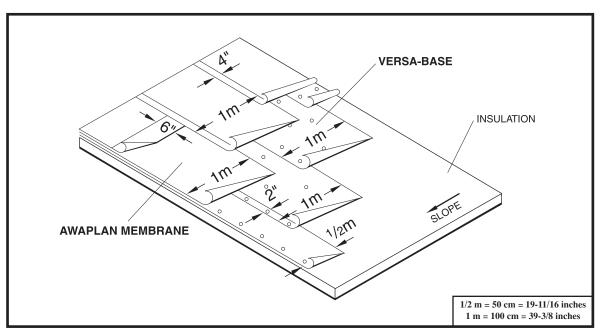

Material Requirements

TAMKO VERSA-BASE® Modified Asphalt Base Sheet	1 ply
TAMKO AWAPLAN PREMIUM FR (Granule Surfaced)	1 ply
Asphalt (Per 100 sq. ft.)	Approx. 46 lbs.

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements

Insulation: The insulation should be installed according to the manufacturer's specification in the thickness required. The insulation should conform to TAMKO requirements. Polyisocyanurate and expanded polystyrene must have an overlay of a minimum 1/2 in. fiberboard, perlite, or fiberglass roof insulation.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, Type III for slopes up to 1/4 in. and Type IV for slopes up to 3 in.

VERSA-BASE Sheet: Starting at the low point of the roof, install 1 ply of TAMKO VERSA-BASE, beginning with a 1/2 m width, then a full 1 m width, side lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Solid mop to the insulation with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the base ply (pressed into the hot asphalt) with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above

400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the base ply by sufficiently heating the back side with a torch at the juncture of the base ply and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica and formaldehyde. Crystalline silica and formaldehyde have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.

Application of product(s) in this specification using "torch applied" or "hot mopped" applications may expose workers and others in the work area to oxidized asphalt and its emissions. The International Agency for Research on Cancer has classified occupational exposures to oxidized asphalt and its emissions during roofing as a "probable human carcinogen." During installation and removal



107FR AWAPLAN PREMIUM FR


INSULATED DECKS

of the product(s) in this specification, including "torch applied" or "hot mopped" application, workers must take precautions to assure adequate ventilation and use effective personal protective equipment to prevent exposures to dusts, fumes, vapors and mists. It is the responsibility of the contractor and workers to protect themselves and others in the work area from exposure to oxidized asphalt and its emissions when applying the product(s) in this specification.



108FR AWAPLAN PREMIUM FR

INSULATED DECKS

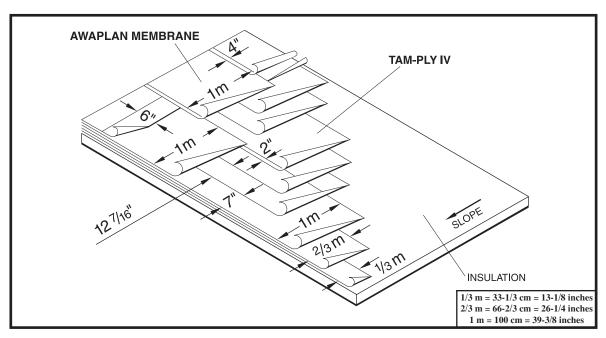

Material Requirements

TAMKO TAM-PLY IV®	
Fiberglass Ply Sheet	3 plies
TAMKO AWAPLAN PREMIUM FR	
(Granule Surfaced)	1 ply
Asphalt (Per 100 sq. ft.)	Approx. 92 lbs.

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements.

Insulation: The insulation should be installed according to the manufacturer's specification in the thickness required. The insulation should conform to TAMKO requirements. Polyisocyanurate and expanded polystyrene must have an overlay of a minimum 1/2 in. fiberboard, perlite, or fiberglass roof insulation.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, **Type III for slopes up to 1/4 in.** and **Type IV for slopes up to 3 in.**

Fiberglass Ply Sheets: Over the insulation, install 3 plies of TAMKO TAM-PLY IV in specification asphalt. Starting from the low point of the roof, apply a 1/3 m width, then a 2/3 m width. Follow with full 1 m widths, shingle fashion, lapping each ply 26-15/16 in. in such a manner so that at least 3 plies of ply sheet cover the insulation at any point. Approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. should be used to embed each ply.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the ply sheet (pressed into the hot asphalt) with approximately 23 lbs. (±15%)

of specification as phalt per $100~\rm sq.$ ft. The asphalt should be above $400^{\rm o}$ F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the ply sheet by sufficiently heating the back side with a torch at the juncture of the ply sheet and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains formaldehyde. Formaldehyde has been classified as a "known" human carcinogen by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.

Application of product(s) in this specification using "torch applied" or "hot mopped" applications may expose workers and others in the work area to oxidized asphalt and its emissions. The International Agency for Research on Cancer has classified occupational exposures to oxidized asphalt and its emissions during roofing as



108FR AWAPLAN PREMIUM FR


INSULATED DECKS

a "probable human carcinogen." During installation and removal of the product(s) in this specification, including "torch applied" or "hot mopped" application, workers must take precautions to assure adequate ventilation and use effective personal protective equipment to prevent exposures to dusts, fumes, vapors and mists. It is the responsibility of the contractor and workers to protect themselves and others in the work area from exposure to oxidized asphalt and its emissions when applying the product(s) in this specification.



109FR AWAPLAN PREMIUM FR

INSULATED DECKS

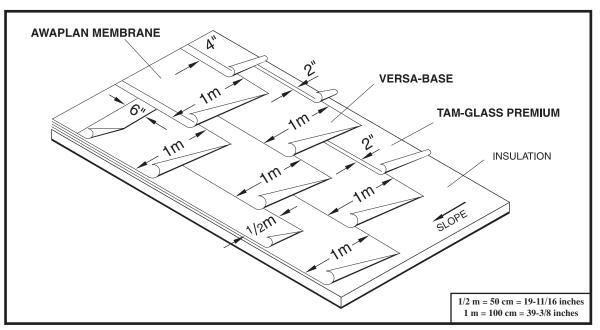

Material Requirements

Asphalt (Per 100 sq. ft.)	Approx. 69 lbs.
(Granule Surfaced)	1 ply
TAMKO AWAPLAN PREMIUM FR	
Base Sheet	1 ply
TAMKO VERSA-BASE®	
Fiberglass Ply Sheet	1 ply
TAMKO TAM-GLASS PREMIUM®	

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements.

Insulation: The insulation should be installed according to the manufacturer's specification in the thickness required. The insulation should conform to TAMKO requirements. Polyisocyanurate and expanded polystyrene must have an overlay of a minimum 1/2 in. fiberboard, perlite, or fiberglass roof insulation.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, **Type III for slopes up to 1/4 in.** and **Type IV for slopes up to 3 in.**

TAM-GLASS PREMIUM: Starting at the low point of the roof, install one ply of TAM-GLASS PREMIUM, side lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Solid mop to the insulation with approximately 23 lbs. ($\pm 15\%$) of specification asphalt per 100 sq. ft.

VERSA-BASE Sheet: Starting at the low point of the roof, install 1 ply of TAMKO VERSA-BASE, beginning with a 1/2 m width, then a full 1 m width, side lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Solid mop to the base ply with approximately 23 lbs. ($\pm 15\%$) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application

and mopped no more than 4 ft. in front of the roll.

Note: It is acceptable to invert the TAM-GLASS PREMIUM and the VERSA-BASE.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the ply sheet (pressed into the hot asphalt) with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the ply sheet by sufficiently heating the back side with a torch at the juncture of the ply sheet and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica and formaldehyde. Crystalline silica and formaldehyde have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal.



109FR AWAPLAN PREMIUM FR


INSULATED DECKS

However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.



111FR AWAPLAN PREMIUM FR

NAILABLE DECKS (GYPSUM AND LIGHTWEIGHT INSULATING CONCRETE)

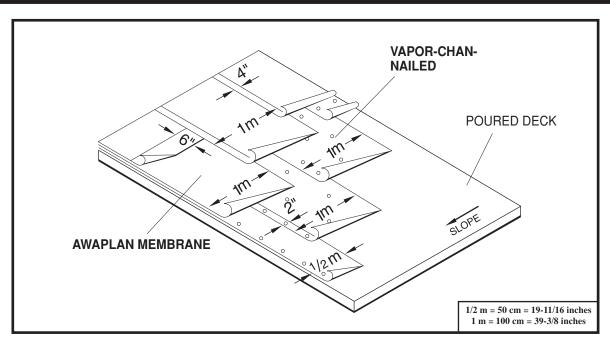

Material Requirements

TAMKO VAPOR-CHAN®	
Fiberglass Venting Asphalt Base Shee	et 1 ply
TAMKO AWAPLAN PREMIUM FR	
(Granule Surfaced)	1 ply
Asphalt (Per 100 sq. ft.)	Approx. 23 lbs.
Clinch-type nails	
for base sheet (per 100 sq ft.)	Approx. 100 nails

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, Type III for slopes up to 1/4 in. and Type IV for slopes up to 3 in.

VAPOR-CHAN: Starting at the low point of the roof, install 1 ply of TAMKO VAPOR-CHAN, beginning with a 1/2 m width, then a full 1 m width, side lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Nail the sheets along the lap at intervals of no more than 8 in. Stagger-nail on 16 in. centers along 2 lines located 13 in. from each edge of the base sheet. For specific fastening patterns for wind uplift listings, contact the Technical Services Department.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the base ply (pressed into the hot asphalt) with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the base ply by sufficiently heating the back side with a torch at the juncture of the base ply and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica and formaldehyde. Crystalline silica and formaldehyde have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.

Application of product(s) in this specification using "torch applied" or "hot mopped" applications may expose workers and others in the work area to oxidized asphalt and its emissions. The International Agency for Research on Cancer has classified occupational exposures to oxidized asphalt and its emissions during roofing as a "probable human carcinogen." During installation and removal of the product(s) in this specification, including "torch applied" or "hot mopped" application, workers must take precautions to assure

For complete information on TAMKO's recommendations and requirements, consult TAMKO's web site at www.tamko.com TAMKO Building Products, Inc., P. O. Box 1404, Joplin, MO $\,$ 64802 $\,$ • 1-800-641-4691 $\,$ • www.tamko.com



111FR AWAPLAN PREMIUM FR


NAILABLE DECKS (GYPSUM AND LIGHTWEIGHT INSULATING CONCRETE)

adequate ventilation and use effective personal protective equipment to prevent exposures to dusts, fumes, vapors and mists. It is the responsibility of the contractor and workers to protect themselves and others in the work area from exposure to oxidized asphalt and its emissions when applying the product(s) in this specification.



112FR AWAPLAN PREMIUM FR

NAILABLE DECKS (WOOD)

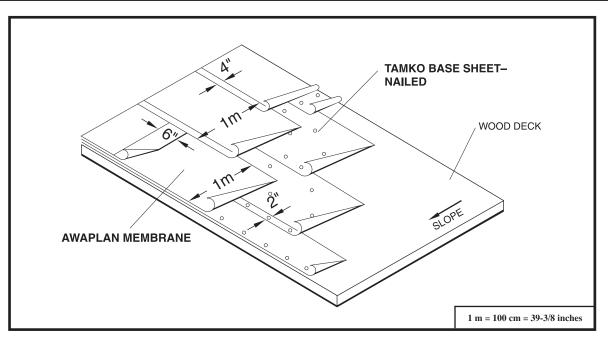

Material Requirements

TAMKO TYPE 43 Coated Base Sheet, TAMKO-GLASS-BASE® or BASE-N-PLY® Base Sheet 1 ply

TAMKO AWAPLAN PREMIUM FR
(Granule Surfaced) 1 ply

Asphalt (Per 100 sq. ft.) Approx. 23 lbs.

Clinch-type nails

for base sheet (per 100 sq ft.) Approx. 100 nails

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, **Type III for slopes up to 1/4 in.** and **Type IV for slopes up to 3 in.**

Base Sheet: Starting at the low point of the roof, install 1 ply of TAMKO TYPE 43 Coated Base Sheet, GLASS-BASE, or BASE-N-PLY, beginning with a 1/2 width, then a full 1 width, side lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Nail GLASS-BASE or BASE-N-PLY sheets along the lap at intervals of no more than 8 in. Stagger-nail on 16 in. centers along 2 lines located 13 in. from each of the base sheet. Nail TYPE 43 Coated Base Sheet along the lap at intervals of no more than 9 in. Stagger-nail on 18 in. centers along 2 lines located 12 in. from each edge of the base sheet. For specific fastening patterns for wind uplift listings, contact the Technical Services Department.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the base ply (pressed into the hot asphalt) with approximately 23 lbs. (±15%)

of specification asphalt per 100~sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the base ply by sufficiently heating the back side with a torch at the juncture of the base ply and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

SAFETY IS OF MAJOR IMPORTANCE WHEN HEAT WELDING MODIFIED BITUMENS ON A WOOD DECK. THERE SHOULD BE A SUFFICIENT NUMBER OF FIRE EXTINGUISHERS ON THE ROOFTO HANDLE ANY CONTINGENCY WHICH MIGHT DEVELOP.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica, formaldehyde and wood dust. Crystalline silica, formaldehyde and wood dust have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent



112FR AWAPLAN PREMIUM FR


NAILABLE DECKS (WOOD)

breathing and contact with skin.



113FR AWAPLAN PREMIUM FR

NAILABLE DECKS (GYPSUM, PRECAST* AND LIGHTWEIGHT INSULATING CONCRETE)

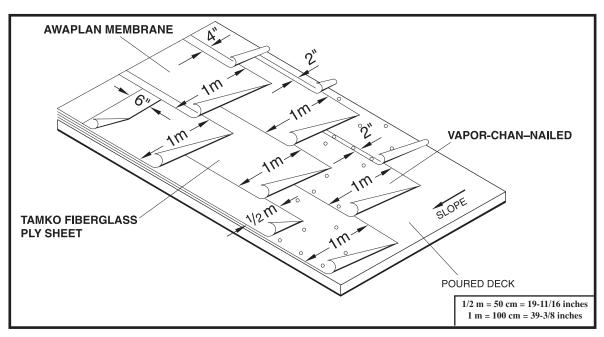

Material Requirements

TAMKO VAPOR-CHAN®	
Fiberglass Venting Asphalt Base S	Sheet 1 ply
TAMKO TAM-GLASS PREMIUM®	or TAM-PLY IV®
Fiberglass Ply Sheet	1 ply
TAMKO AWAPLAN PREMIUM	FR
(Granule Surfaced)	1 ply
Asphalt (Per 100 sq. ft.)	Approx. 46 lbs.
Clinch-type nails	
for base sheet (per 100 sq ft.)	Approx. 100 nails

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, Type III for slopes up to 1/4 in. and Type IV for slopes up to 3 in.

VAPOR-CHAN: Starting at the low point of the roof, install 1 ply of TAMKO VAPOR-CHAN, side lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Nail the sheets along the lap at intervals of no more than 8 in. Stagger-nail on 16 in. centers along 2 lines located 13 in. from each edge of the base sheet. For specific patterns for wind uplift listings, contact the Technical Services Department.

Fiberglass Ply Sheet: Starting at the low point of the roof, install a 1/2 m width, then a full 1 m width of TAM-GLASS PREMIUM or TAM-PLY IV, side-lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Solid mop to the base ply with approximately 23 lbs. ($\pm 15\%$) of specification asphalt.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the ply sheet (pressed into the hot asphalt) with approximately 23 lbs. ($\pm 15\%$) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the ply sheet by sufficiently heating the back side with a torch at the juncture of the ply sheet and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica and formaldehyde. Crystalline silica and formaldehyde have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.

For complete information on TAMKO's recommendations and requirements, consult TAMKO's web site at www.tamko.com TAMKO Building Products, Inc., P. O. Box 1404, Joplin, MO $\,$ 64802 $\,$ • 1-800-641-4691 $\,$ • www.tamko.com



113FR AWAPLAN PREMIUM FR

NAILABLE DECKS (GYPSUM, PRECAST* AND LIGHTWEIGHT INSULATING CONCRETE)


Application of product(s) in this specification using "torch applied" or "hot mopped" applications may expose workers and others in the work area to oxidized asphalt and its emissions. The International Agency for Research on Cancer has classified occupational exposures to oxidized asphalt and its emissions during roofing as a "probable human carcinogen." During installation and removal of the product(s) in this specification, including "torch applied" or "hot mopped" application, workers must take precautions to assure adequate ventilation and use effective personal protective equipment to prevent exposures to dusts, fumes, vapors and mists. It is the responsibility of the contractor and workers to protect themselves and others in the work area from exposure to oxidized asphalt and its emissions when applying the product(s) in this specification.

*Precast Concrete Decks: This specification may be utilized over a precast concrete deck when joints are taped and the VAPOR-CHAN is installed in spot moppings of specification asphalt spaced on (not to exceed) 24 in. centers.



114FR AWAPLAN PREMIUM FR

NAILABLE DECKS (WOOD)

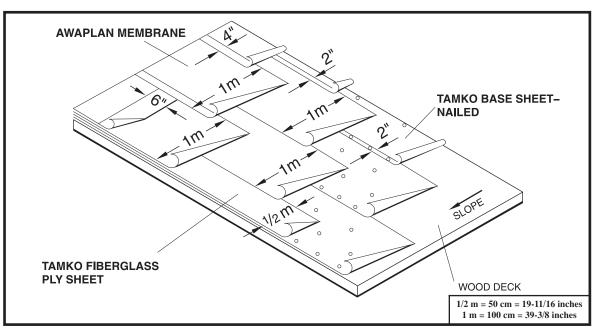

Material Requirements

TAMKO TYPE 43 Coated Base Sheet, TAMKO-GLASS-BASE® or BASE-N-PLY® Base Sheet 1 ply
TAMKO TAM-GLASS PREMIUM® or TAM-PLY IV®
Fiberglass Ply Sheet 1 ply
TAMKO AWAPLAN PREMIUM FR
(Granule Surfaced) 1 ply
Asphalt (Per 100 sq. ft.) Approx. 46 lbs.
Clinch-type nails
for base sheet (per 100 sq ft.) Approx. 100 nails

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

 $\boldsymbol{Deck:}$ The deck should conform to TAMKO general requirements.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, **Type III for slopes up to 1/4 in.** and **Type IV for slopes up to 3 in.**

Base Sheet: Starting at the low point of the roof, install 1 ply of TAMKO TYPE 43 Coated Base Sheet, GLASS-BASE, or BASE-N-PLY, side lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Nail GLASS-BASE or BASE-N-PLY sheets along the lap at intervals of no more than 8 in. Stagger-nail on 16 in. centers along 2 lines located 13 in. from each of the base sheet. Nail TYPE 43 Coated Base Sheet along the lap at intervals of no more than 9 in. Stagger-nail on 18 in. centers along 2 lines located 12 in. from each edge of the base sheet. For specific fastening patterns for wind uplift listings, contact the Technical Services Department.

Fiberglass Ply Sheet: Starting at the low point of the roof, install a 1/2 m width, then a full 1 m width of TAM-GLASS PREMIUM or TAM-PLY IV, side-lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Solid mop to the base ply with approximately 23 lbs. ($\pm 15\%$) of specification asphalt.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the ply sheet (pressed into the hot asphalt) with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the ply sheet by sufficiently heating the back side with a torch at the juncture of the ply sheet and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

SAFETY IS OF MAJOR IMPORTANCE WHEN HEAT WELDING MODIFIED BITUMENS ON A WOOD DECK. THERE SHOULD BE A SUFFICIENT NUMBER OF FIRE EXTINGUISHERS ON THE ROOF TO HANDLE ANY CONTINGENCY WHICH MIGHT DEVELOP.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica, formaldehyde and wood dust. Crystalline silica, formaldehyde and wood dust have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational



114FR AWAPLAN PREMIUM FR


NAILABLE DECKS (WOOD)

exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.



117FR AWAPLAN PREMIUM FR

NAILABLE DECKS (GYPSUM, PRECAST* AND LIGHTWEIGHT INSULATING CONCRETE)

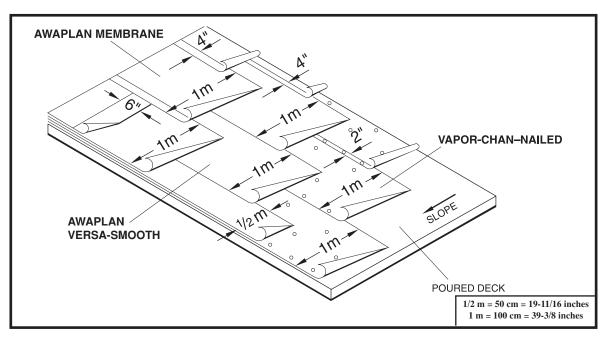

Material Requirements

Clinch-type nails for base sheet (per 100 sq ft.)	Approx. 100 nails
Asphalt (Per 100 sq. ft.)	Approx. 46 lbs.
TAMKO AWAPLAN PREMIUM (Granule Surfaced)	FR 1 ply
TAMKO AWAPLAN VERSA-SMOO	OTH 1 ply
TAMKO VAPOR-CHAN® Fiberglass Venting Asphalt Base S	Sheet 1 ply

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, Type III for slopes up to 1/4 in. and Type IV for slopes up to 3 in.

VAPOR-CHAN: Starting at the low point of the roof, install 1 ply of TAMKO VAPOR-CHAN, side lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Nail the sheets along the lap at intervals of no more than 8 in. Stagger-nail down the center of the sheet on 16 in. centers along 2 lines located 13 in. from each edge of the base sheet. For specific patterns for wind uplift listings, contact the Technical Services Department.

AWAPLAN VERSA-SMOOTH: Starting at the low point of the roof, install 1 ply of TAMKO AWAPLAN VERSA-SMOOTH, beginning with a 1/2 m width, then a full 1 m width, side lapped 4 in. and end lapped 6 in. Apply at a right angle to the slope of the roof. The AWAPLAN VERSA-SMOOTH should be solidly adhered to the base ply (pressed into the hot asphalt) with approximately 23 lbs. ($\pm 15\%$) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no

more than 4 ft. in front of the roll.

Alternately, the AWAPLAN VERSA-SMOOTH can be heat welded and should be solidly adhered to the base ply by sufficiently heating the back side with a torch at the juncture of the base ply and the AWAPLAN VERSA-SMOOTH roll to form a bead of melted asphalt as the AWAPLAN VERSA-SMOOTH is rolled out.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the ply sheet (pressed into the hot asphalt) with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the ply sheet by sufficiently heating the back side with a torch at the juncture of the ply sheet and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica and formaldehyde. Crystalline silica and formaldehyde have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical

For complete information on TAMKO's recommendations and requirements, consult TAMKO's web site at www.tamko.com TAMKO Building Products, Inc., P. O. Box 1404, Joplin, MO 64802 • 1-800-641-4691 • www.tamko.com



117FR AWAPLAN PREMIUM FR

NAILABLE DECKS (GYPSUM, PRECAST* AND LIGHTWEIGHT INSULATING CONCRETE)

nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.


Application of product(s) in this specification using "torch applied" or "hot mopped" applications may expose workers and others in the work area to oxidized asphalt and its emissions. The International Agency for Research on Cancer has classified occupational exposures to oxidized asphalt and its emissions during roofing as a "probable human carcinogen." During installation and removal of the product(s) in this specification, including "torch applied" or "hot mopped" application, workers must take precautions to assure adequate ventilation and use effective personal protective equipment to prevent exposures to dusts, fumes, vapors and mists. It is the responsibility of the contractor and workers to protect themselves and others in the work area from exposure to oxidized asphalt and its emissions when applying the product(s) in this specification.

*Precast Concrete Decks: This specification may be utilized over a precast concrete deck when joints are taped and the VAPOR-CHAN is installed in spot moppings of specification asphalt spaced on (not to exceed) 24 in. centers.



135FR AWAPLAN PREMIUM FR

RECOVER OVER EXISTING GRAVEL SURFACED MEMBRANE OR SMOOTH SURFACED MEMBRANE

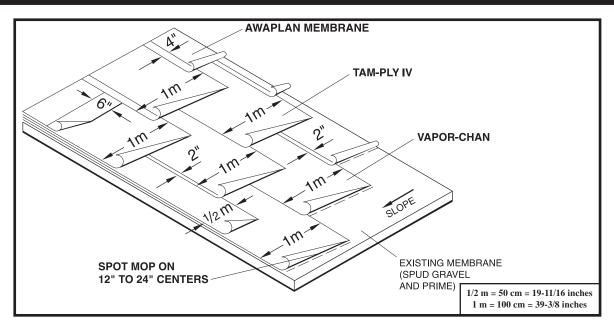

Material Requirements

TAMKO VAPOR-CHAN®	
Fiberglass Venting Base Sheet	1 ply
TAMKO TAM-PLY IV®	
Fiberglass Ply Sheet	1 ply
TAMKO AWAPLAN PREMIUM FR	1 ply
Interply Asphalt (Per 100 sq. ft.)	Approx. 46 lbs.
Concrete Primer (Per 100 sq. ft.)	Approx. 3/4 gal.

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN membrane is required.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, Type III for slopes up to 1/4 in. and Type IV for slopes up to 3 in.

Preparation: Spud the membrane surface and remove all loose roofing gravel and debris. Make random cuts or breaks in the old membrane 4 ft. o.c. to allow vapor pressure to vent. All wet or deteriorated insulation or membrane must be removed and replaced prior to the application of new roofing materials. The surface should be primed with concrete primer at a rate of approximately 3/4 gal. per 100 sq. ft. prior to the application of new roofing materials.

VAPOR-CHAN: Over the old membrane and starting at the low point of the roof, install 1 ply of TAMKO VAPOR-CHAN Base Sheet. The VAPOR-CHAN should be side lapped 2 in. and end lapped 4 in. The base ply should be secured to the old membrane with spots of Type III, Steep Asphalt spaced on (not to exceed) 24 in centers

TAM-PLY IV: Starting at the low point of the roof, install 1 ply of TAM-PLY IV, beginning with a 1/2 m width, then a full 1 m width, side-lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Solid mop to the base ply with approximately 23 lbs. ($\pm 15\%$) of specification asphalt per 100 sq. ft.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 ply of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the ply sheet (pressed into the hot asphalt) with approximately 23 lbs. ($\pm 15\%$) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the ply sheet by sufficiently heating the back side with a torch at the juncture of the ply sheet and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

Venting: One-way roof vents may be placed at a minimum of 1 vent for each 10 squares of roof area.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica and formaldehyde. Crystalline silica and formaldehyde have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification.



135FR AWAPLAN PREMIUM FR


RECOVER OVER EXISTING GRAVEL SURFACED MEMBRANE OR SMOOTH SURFACED MEMBRANE

Take precautions to prevent breathing and contact with skin.



136FR AWAPLAN PREMIUM FR

RECOVER OVER EXISTING GRAVEL SURFACED MEMBRANE (COAL-TAR PITCH)

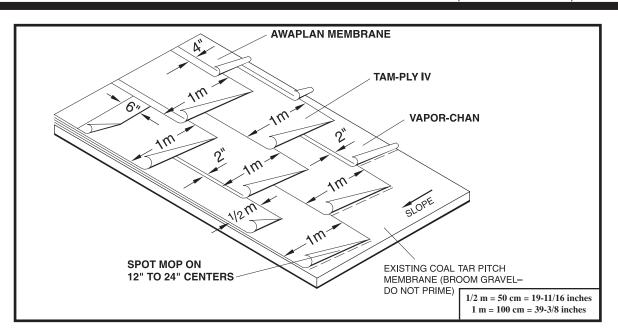

Material Requirements

TAMKO VAPOR-CHAN® Fiberglass Venting Asphalt Base Sheet	1 ply
TAMKO TAM-PLY IV® Fiberglass Ply Sheet	1 ply
TAMKO AWAPLAN PREMIUM FR	1 ply
Interply Asphalt (Per 100 sq. ft.)	Approx. 46 lbs.

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above** 3/4 in. per linear ft., fastening of the AWAPLAN membrane is required.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, Type III for slopes up to 1/4 in. and Type IV for slopes up to 3 in.

Preparation: Broom the membrane surface and remove all loose roofing gravel and debris. Make random cuts or breaks in the old membrane 4 ft. o.c. to allow vapor pressure to vent from the old system and any existing insulation materials. All wet or deteriorated insulation or membrane must be removed and replaced prior to the application of new roofing materials. DO NOT USE ANY PRIMERS.

VAPOR-CHAN: Over the old membrane and starting at the low point of the roof, install 1 ply of TAMKO VAPOR-CHAN Base Sheet. The VAPOR-CHAN should be side lapped 2 in. and end lapped 4 in. The base ply should be secured to the old membrane with spots of Type III, Steep Asphalt spaced on (not to exceed) 24 in. centers.

TAM-PLY IV: Starting at the low point of the roof, install 1 ply of TAM-PLY IV, beginning with a 1/2 m width, then a full 1 m width, side-lapped 2 in. and end lapped 4 in. Apply at a right angle to the slope of the roof. Solid mop to the base ply with approximately 23 lbs. $(\pm 15\%)$ of specification asphalt per 100 sq. ft.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 ply of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the ply sheet (pressed into the hot asphalt) with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the ply sheet by sufficiently heating the back side with a torch at the juncture of the ply sheet and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

Venting: One-way roof vents may be placed at a minimum of 1 vent for each 10 squares of roof area.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica and formaldehyde. Crystalline silica and formaldehyde have been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation



136FR AWAPLAN PREMIUM FR


RECOVER OVER EXISTING GRAVEL SURFACED MEMBRANE (COAL-TAR PITCH)

or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.



146FR AWAPLAN PREMIUM FR

INSULATED DECK

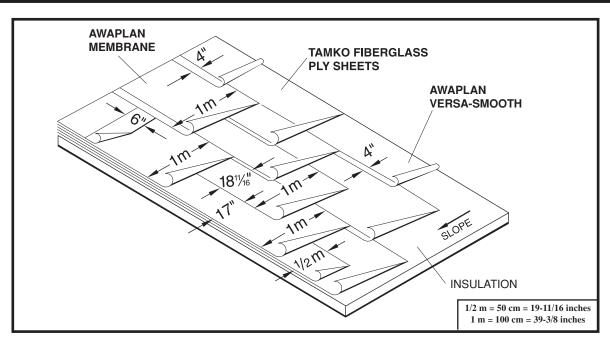

Material Requirements

TAMKO AWAPLAN VERSA SMOOTH

TAMKO TAM-PLY® OR TAM-GLASS PREMIUM® Fiberglass Ply Sheet 2 plies

TAMKO AWAPLAN PREMIUM FR (Granule Surfaced)

1 ply

Interply Asphalt (per 100 sq ft.)

Approx. 92 lbs.

Slope: Positive drainage up to 3 in. per linear ft. **For slopes above 3/4 in. per linear ft.,** fastening of the AWAPLAN PREMIUM FR is required.

Deck: The deck should conform to TAMKO general requirements.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, Type III for slopes up to 1/4 in. and Type IV for slopes up to 3 in.

Insulation: The insulation should be installed according to the manufacturer's specification in the thickness required. The insulation should conform to TAKO requirements. Polyisocyanurate and expanded polystyrene must have an overlay of a minimum 1/2 in. fiberboard, perlite, or fiberglas roof insulation.

Asphalt: The asphalt should be certified by the manufacturer to meet ASTM D-312, Type III for slopes up to 1/4 in. and Type IV for slopes up to 3 in.

AWAPLAN VERSA-SMOOTH: Starting at the low point of the roof, install 1 ply of TAMKO AWAPLAN VERSA-SMOOTH, begining with a full 1 m width, side lapped 4 in. and end lapped 6 in. Apply at a right angle to the slope of the roof. The AWAPLAN VERSA-SMOOTH should be solidly adhered to the insulation (pressed into the hot asphalt) with approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. The asphalt should be above 400°F at the point of application and mopped no more than 4 ft.

in front of the roll.

Alternately, the AWAPLAN VERSA-SMOOTH can be heat welded and should be solidly adhered to the insulation by sufficiently heating the back side with a torch at the juncture of the insulation and the AWAPLAN VERSA-SMOOTH roll to form a bead of melted asphalt as the AWAPLAN VERSA-SMOOTH is rolled out.

Fiberglass Ply Sheets: Over the base ply, install **2 plies** of TAM-PLY IV or TAM-GLASS PREMIUM Fiberglass Ply Sheet in specification asphalt. Start with an 1/2 m wide sheet followed by full 1 m widths, shingle fashion, lapping eah ply 20-11/16 in. over the preceding ply so that at least 2 plies cover the base ply at any point. Approximately 23 lbs. (±15%) of specification asphalt per 100 sq. ft. should be used to embed each ply.

AWAPLAN PREMIUM FR: Starting at the low point of the roof, install 1 layer of TAMKO AWAPLAN PREMIUM FR granule surfaced sheet, side lapped 4 in. and end lapped 6 in. The AWAPLAN PREMIUM FR should be solidly adhered to the ply sheet (pressed into the hot asphalt) with approximately 23 lbs. ($\pm 15\%$) of specification asphalt per 100 sq. ft. The asphalt should be above 400° F at the point of application and mopped no more than 4 ft. in front of the roll.

Alternately, the AWAPLAN PREMIUM FR can be heat welded and should be solidly adhered to the ply sheet by sufficiently heating the back side with a torch at the juncture of the ply sheet and the AWAPLAN PREMIUM FR roll to form a bead of melted asphalt as the AWAPLAN PREMIUM FR is rolled out. Use care when applying heat as damage can occur to the product by overheating.

Flashing: The flashing material **must** be a TAMKO polyester reinforced modified asphalt flashing material.

U.L. Requirements: Contact TAMKO for information on U.L. systems requirements.

Caution: A product(s) in this specification contains crystalline silica and formaldehyde. Crystalline silica and formaldehyde have



146FR AWAPLAN PREMIUM FR

INSULATED DECK

been classified as "known" human carcinogens by the International Agency for Research on Cancer (IARC) and the National Toxicology Program. A product(s) in this specification also contains oxidized asphalt. Occupational exposures to oxidized asphalt and its emissions during roofing have been classified by IARC as a "probable human carcinogen". Oxidized asphalt also contains Polycyclic Aromatic Hydrocarbons some of which have been classified by IARC as known or probable human carcinogens. The physical nature of the product(s) in this specification may help limit any inhalation or dermal hazard during application and/or removal. However, physical forces such as sawing, grinding or drilling during demolition work and heating or burning may increase the inhalation or dermal exposure hazard of the product(s) in this specification. Take precautions to prevent breathing and contact with skin.